

# Laser-Assisted Preparation of Polycarbonate/TiO<sub>2</sub> Mesh and its Hydrophobicity Improvement Using Octadecylamine

Soheil Mohammadtaheri<sup>a</sup>, Babak Jaleh<sup>a,\*</sup>, Mahtab Eslamipناه<sup>a</sup>, Niloufar pakzad Afshar<sup>b</sup>, and Saeid Azizian<sup>c</sup>

<sup>a</sup>Department of Physics, Faculty of Science, Bu-Ali Sina University, Hamedan, Iran

<sup>b</sup>Department of Physics, Faculty of Science, Urmia University, Urmia, Iran

<sup>c</sup>Department of Physical Chemistry, Faculty of Chemistry and Petroleum Sciences, Bu-Ali Sina University, Hamedan, Iran

Corresponding author email: [jaleh@basu.ac.ir](mailto:jaleh@basu.ac.ir)

Received: Sept. 02, 2025, Revised: Jan. 06, 2026, Accepted: Feb. 23, 2026, Available Online: Feb. 25, 2026, DOI: will be added soon

**ABSTRACT**— The present research aims to combine rapid and modern laser drilling with loading octadecylamine (ODA) to produce a hydrophobic polycarbonate/TiO<sub>2</sub> mesh. The laser drilling first created hierarchical microholes on the polycarbonate/TiO<sub>2</sub> film using ablation process. The polycarbonate/TiO<sub>2</sub> mesh was then immersed in ODA solution. The morphological and structural investigation indicated that ODA shells cover the PC-TiO<sub>2</sub> mesh surface. X-ray photoelectron spectroscopy (XPS) was utilized for investigating the change in element/chemical state after laser drilling and ODA treatment. The wettability of the produced polycarbonate/TiO<sub>2</sub> mesh was changed from hydrophilic to hydrophobic, in a way that the water contact angle was changed from 45 to 122.4°.

**KEYWORDS:** Hydrophobic, Laser drilling, Polycarbonate, TiO<sub>2</sub>.

## I. INTRODUCTION

In the last decade, polymeric meshes have been noticed due to their biocompatibility, mechanical properties and light weight [1]. They are widely utilized to develop materials for tissue engineering, drug delivery and filtration. They can also be employed for electronic devices preparation, electromagnetic interface shielding and designing electrodes for electrochemical applications [2]. These polymeric structures can be generated from

different polymer nanocomposites [3]. Polymeric nanocomposites, including polymer matrix and nanofiller, are attracting attention due to their unique chemical properties and light weight. They have significant mechanical and physical stability due to the presence of large interfacial area between the polymer matrix and nanofillers. The presence of nanofillers such as carbon-based and semiconductor nanoparticles (NPs) can enhance the mechanical and physical properties of polymers. The presence of nanofillers leads to an increase in chemical activation of the polymer matrix due to their high surface area. Polymeric nanocomposites can be produced through different methods such as mechanical mixing, solution dispersion and the sol-gel method [4]-[7].

Polycarbonate (PC) is an attractive polymer with remarkable transparency in the visible spectral range. It is introduced as a great replacement for glasses in different applications. It is used as an accurate optical element [8,9]. It has shown significant properties such as high chemical resistance, good heat resistance, facile shapeable and water resistance [10]. However, PC has demonstrated poor physical properties, such as low hardness and photocorrosion resistance, which limit its applications. Therefore, it needs

to be modified for improving or changing its properties, which can be realized by adding nanofillers [11]-[15].

Nanofillers can be organic or inorganic in nature, in which semiconductor nanomaterials such as SiO<sub>2</sub> and TiO<sub>2</sub> are the most common nanofillers for developing polymer properties. They are easily available or synthesized. Adding nanoparticles (NPs) can provide thermal and mechanical stability. Among these, TiO<sub>2</sub> NPs gained attention due to their non-toxicity, availability, corrosion resistance and cost-effectiveness properties. It is also chemically inert and possesses a high refractive index and high hardness. TiO<sub>2</sub> nanofiller affords unique optical, electrical and physicochemical features even at low concentrations, making polymer-TiO<sub>2</sub> nanostructures as a practical material for applications in solar cells, gas sensors, photocatalysis and drug delivery [16-18]. TiO<sub>2</sub> can be found in three different metastable phases of rutile, anatase, and brookite, which define its properties. For example, different phases of TiO<sub>2</sub> have different bandgap values; rutile phase has a bandgap of 3 eV, while anatase has 3.2 eV [19]. It possesses low free energy of surface and can improve the wettability behavior of the surface [20]. Degussa P25 TiO<sub>2</sub> has been a standard material, which is a biphasic TiO<sub>2</sub>, including mixed anatase and rutile phases. These nanoparticles possess significant properties, including small particle size, large specific surface area and high crystallinity [21].

Surface wettability is an important behavior of polymer materials that has attracted a lot of attention in material research. Surface wettability is also well-known as a significant characteristic of materials for specifying their applications, which strongly depends on surface properties such as chemical compounds and surface morphology. Surfaces with different wettability degree lead to unique properties and applications such as corrosion resistance, self-cleaning, liquid separation, de-icing and non-fouling. Wettability degree is determined by measuring the contact angle (CA) between the wetting liquid and the solid

substrate. The CA less than 90° is shows a hydrophilic surface, while a hydrophobic surface is introduced with a CA higher than 90° [22]. In comparison with hydrophilic surfaces, hydrophobic surfaces have attracted a lot of attention in basic research. They can be applied in particular application fields such as self-cleaning, antibacterial, preparation of waterproof and anti-fogging glass, anti-adhesion and oil/water separation. Different materials such as mesh, polymeric films and textiles can be employed to fabricate hydrophobic surfaces [23]-[26]. However, the number of hydrophilic surfaces is more than hydrophobic surfaces. A hydrophobic surface can be manufactured by using low-surface-energy materials or by creating a rough structure on the materials with low-surface energy. According to reports, there are different approaches for fabricating hydrophobic surfaces, such as anodic oxidation, electrodeposition, chemical vapor deposition, sol-gel, laser ablation and spin-coating [27]-[33]. Octadecylamine (ODA) possesses low surface energy due to its long alkyl chain and has been widely used to improve hydrophobicity [34, 35]. For instance, in 2020, Sun et al. produced a hydrophobic coating (ODA-polyphenol film) through one-step spraying co-deposition [36]. They reported that the ODA modification enhances the hydrophobicity of poly(tannic acid) and poly(pyrogallol). The ODA was also used for the treatment of nylon by Du et al in 2015 [34]. They immersed nylon fabric treated by poly(acrylic acid)/tetraethylorthosilicate at room temperature for 2 h. The reaction between amino groups of ODA and carboxyl groups of nylon enhanced the hydrophobicity of the nylon. Fig. 1 shows a schematic of ODA structure on the mesh substrate.

Recently, laser processing has been widely employed for modifying surface properties of a wide range of materials [37]. It can be used to modify the surface of polymers and change the surface energy and CA value [38]. Laser ablation can provide a controllable and cost-effective technique for fabricating stable micro/nano hierarchical structures on different materials and drill targets with narrow

damaging effects for producing mesh. Laser beam drilling, a thermal energy machining process, is the most attractive technique for drilling wide range of materials such as ceramics, metals and polymers. It is introduced as a high-speed and accurate method for modifying materials with high efficiency [39-42]. Different types of lasers such as CO<sub>2</sub>, Nd:YAG and fiber laser have been utilized for this purpose [42]-[44]. The laser beam drilling has been successfully used for preparing polymer meshes. For instance, Abdulwahab et al. created micro-holes on the PC and poly methyl methacrylic using CO<sub>2</sub> laser source [45]. They investigated the effect of laser power, exposure time and focal plane position on the holes. In another report, a femtosecond pulsed laser was used to form controlled micro-hole arrays on the PC sheet [46].

The laser beam drilling is based on the laser ablation mechanisms, which consists of two vaporization and melt expulsion processes. The surface electrons of the target are excited by focusing and hitting the laser beam, leading to generate heat. Light intensity and target thickness are effective in the absorption of light. The heat creates melting or vaporization of the target, forming a plasma plume. The melted or vaporized materials are removed by plasma expansion, making accurate holes. The scraped materials deposit around the holes. Therefore, it can be used to produce a mesh sheet [47, 48].

In this report, a hydrophobic polymeric mesh was provided through a simple and low-cost method of laser drilling followed by ODA coating. The TiO<sub>2</sub> NPs were firstly dispersed in the PC matrix by magnetic stirring and PC-TiO<sub>2</sub> nanocomposite films were acquired after drying at 40 °C. The laser drilling method was utilized to obtain PC-TiO<sub>2</sub> mesh. This process provided hierarchical microholes on the film. The ODA solution was then used to change the wettability of PC-TiO<sub>2</sub> mesh. The presence of ODA with shell-like morphology did not close the holes of the polymeric mesh and created a hydrophobic surface.

## II. EXPERIMENTAL PROCEDURE

### A. Material and Instruments

TiO<sub>2</sub> NPs with anatase and rutile phases were fabricated from the Degussa Co. and used as nanofiller. PC was also purchased from General Electric Company of America. The crystalline structure of PC-TiO<sub>2</sub> film was surveyed using X-ray diffraction (XRD, ITALSTRUCTURE) pattern. Wettability of PC and PC-TiO<sub>2</sub> nanocomposite film was examined by measuring water contact angle. The surface chemical features were identified via X-ray photoelectron spectroscopy (XPS, X250i), in which all the binding energy was calibrated by the characteristic carbon feature C1s = 284.7 eV. The surface changes in PC and PC-TiO<sub>2</sub> mesh after ODA treatment were determined by scanning electron microscopy (SEM, JEOL-JSM-840A) images.

### B. Preparation of PC-TiO<sub>2</sub> Nanocomposite Film

To fabricate PC-TiO<sub>2</sub> nanocomposite film, 1 g of PC was dissolved in 30 ml of dichloromethane by magnetic stirring at ambient conditions. Different masses of TiO<sub>2</sub> NPs (0.01, 0.02, 0.03 and 0.05 g) were dispersed in 10 ml dichloromethane by sonication for 60 min. When the TiO<sub>2</sub> NPs suspension was stirred, the PC solution was slowly added to it, preventing the precipitation of TiO<sub>2</sub> NPs and penetrating PC into the spaces between the NPs. Afterwards, the prepared suspension was poured into a circular glass template with diameter of 7 cm and dried at 40 °C for 6 h.

### C. Preparation of PC-TiO<sub>2</sub>/ODA Mesh

A fiber laser (RFL-P30Q) with maximal power of 30 W, wavelength of 1064 nm and frequency of 20 kHz was used to drill the PC-TiO<sub>2</sub> nanocomposite film. The holes were designed with a diameter of 160 μm and the edge-to-edge distances of 340 and 400 μm. A laser beam with power of 9 W, scanning speed of 3000 mm/s and 2 scanning loops was focused on the PC-TiO<sub>2</sub> surface and the polymeric nanocomposite was hacked line-by-line with scanning line distance of 0.01 mm. Finally, a regular arrangement of holes was

obtained and the samples were named as PC-TiO<sub>2</sub>-laser.

To improve hydrophobicity of PC-TiO<sub>2</sub> mesh, ODA ethanolic solutions with different weight percentages 0.01 wt.%, 0.02 wt.%, 0.03 wt.% and 0.05 wt.% were prepared. The obtained solution was then heated at temperature of 60°C and the PC-TiO<sub>2</sub> mesh was immersed in ODA solution for different times of 5, 10, 15, 30, 45, 60 and 90 min. At last, the PC-TiO<sub>2</sub> mesh impregnated with ODA was dried at ambient conditions for 2 h and named as PC-yTiO<sub>2</sub>/ODA-x-laser (y and x are TiO<sub>2</sub> weight and immersing time, respectively). For comparison, PC-TiO<sub>2</sub> immersed in ODA was also prepared and labeled as PC-yTiO<sub>2</sub>/ODA-x.

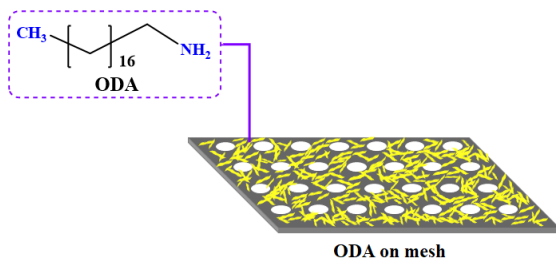


Fig. 1. The structure of ODA on the mesh substrate.

### III. RESULTS AND DISCUSSIONS

As mentioned, PC-TiO<sub>2</sub> nanocomposite films with different weight percentages were prepared. Among these samples, preliminary observations revealed that the film containing 5 wt.% TiO<sub>2</sub> was brittle, while the 1 wt.% and 2 wt.% samples did not form a mesh structure under laser irradiation, and pores did not appear in some regions. This behavior can be attributed to the fact that, at low concentrations, the samples behave similarly to pure polycarbonate. Therefore, the sample including 0.03 g TiO<sub>2</sub> was selected as the best sample.

Figure 2 indicates the XRD patterns of PC-TiO<sub>2</sub>, PC-0.03TiO<sub>2</sub>/ODA-90 and PC-0.03TiO<sub>2</sub>/ODA-90-laser nanocomposite films. The observed peak with the maximal intensity at about 17.1° reveals the amorphous nature of PC [49, 50]. The peaks located at 25.4°, 37.9°, 48.2°, 54.2°, 55.2° and 63° are due to the presence of anatase phase of TiO<sub>2</sub> (JCPDS 04-

0477). Two peaks with low intensity at 27.5° and 69.1° are attributed to the rutile phase of TiO<sub>2</sub> (JCPDS 21-1276). It is clear that anatase is the main phase of TiO<sub>2</sub> NPs. The low intensity of TiO<sub>2</sub> peaks is related to the low concentration of TiO<sub>2</sub> NPs in the PC matrix. The XRD profile of PC-TiO<sub>2</sub>/ODA is similar to PC-TiO<sub>2</sub> and a tiny shift can be observed in the PC peak (from 17.1° to 17.9°), suggesting no change in the PC-TiO<sub>2</sub> structure. The degree of sample crystallinity has declined in PC-TiO<sub>2</sub>/ODA-laser XRD pattern, which is probably due to material ablation.

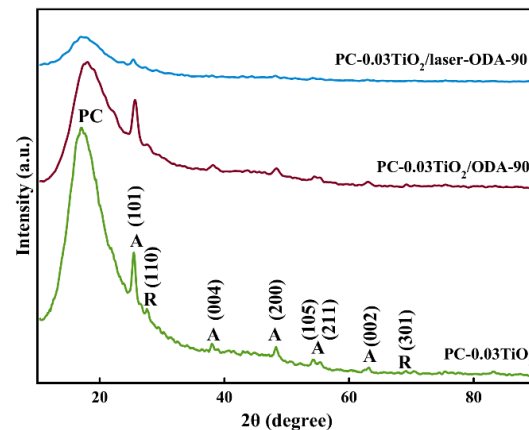


Fig. 2. XRD pattern of PC-0.03TiO<sub>2</sub>, PC-0.03TiO<sub>2</sub>/ODA-90 and PC-0.03TiO<sub>2</sub>/ODA-90-laser.

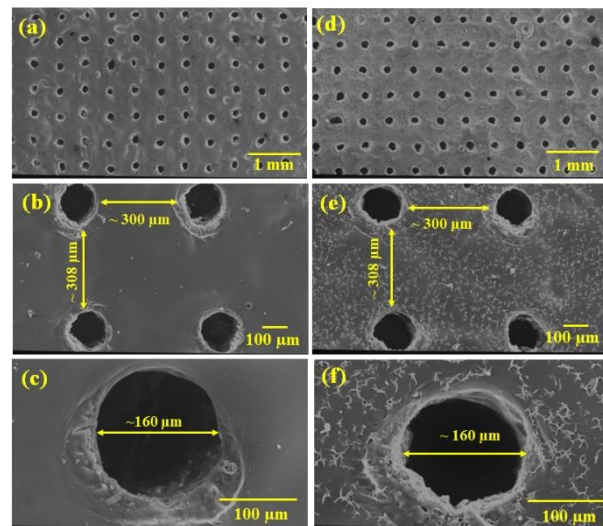
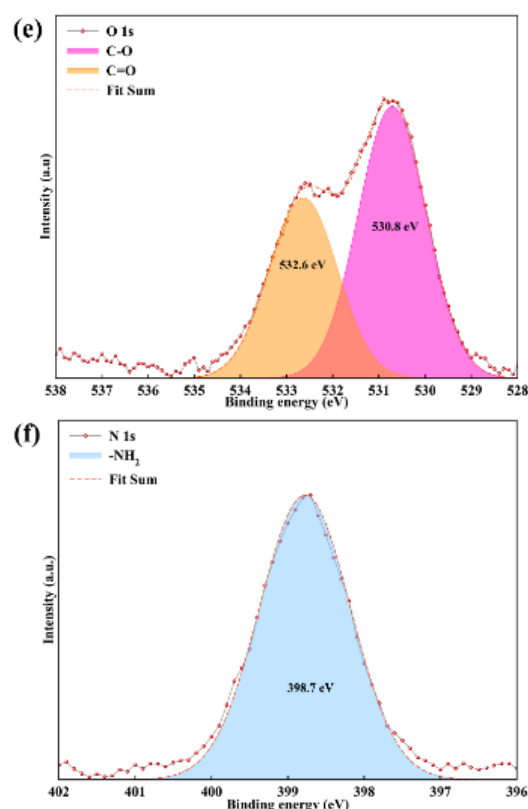
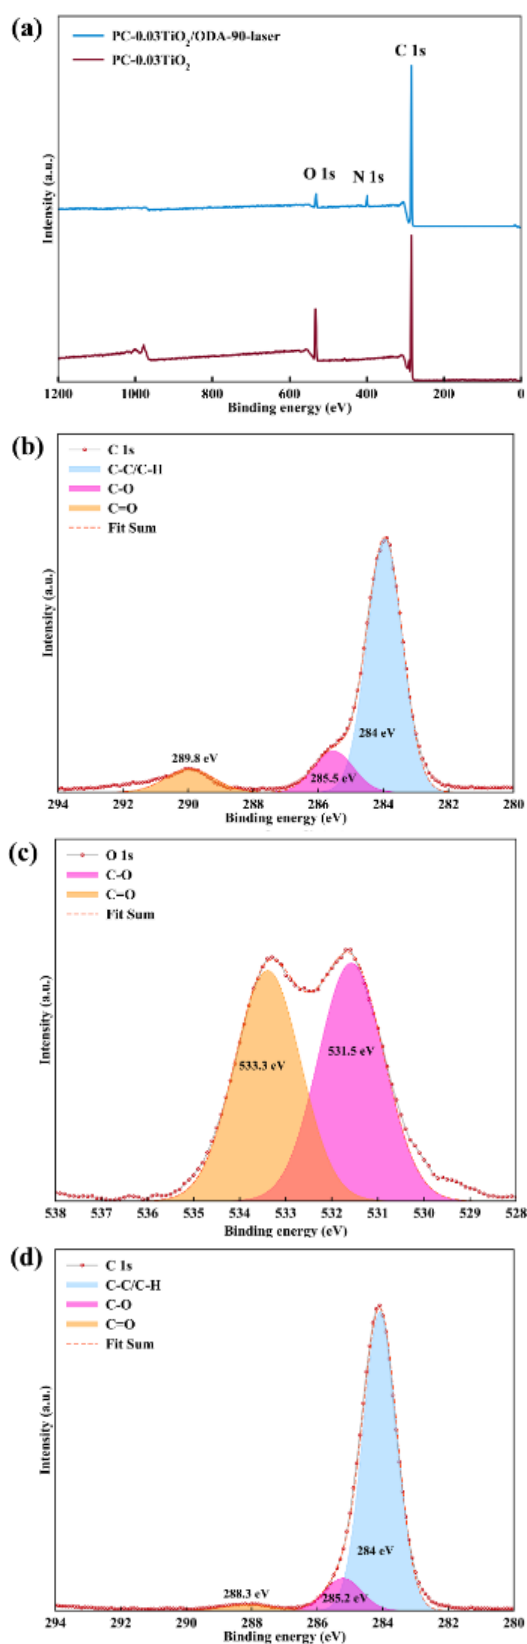


Fig. 3. SEM images of (a-c) PC-0.03TiO<sub>2</sub> mesh and (d-f) PC-0.03TiO<sub>2</sub>/ODA-90-laser.

SEM images at different magnifications have been used to identify the morphology of samples. Fig. 3(a-c) indicates a regular array of holes on the flat PC-TiO<sub>2</sub>. A cover of ODA shells on the PC-TiO<sub>2</sub> mesh can be observed

in Fig. 3(d-f). It is clear that holes are not closed with ODA.



**Fig. 4.** (a) XPS spectra of PC-0.03TiO<sub>2</sub> and PC-0.03TiO<sub>2</sub>/ODA-90-laser, high-resolution XPS spectrum of (b) C1s and (c) O1s of PC-0.03TiO<sub>2</sub>, high-resolution XPS spectrum of (d) C1s, (e) O1s and (f) N1s of PC-0.03TiO<sub>2</sub>/ODA-90-laser.

XPS analyses were employed to identify chemical bindings of PC-0.03TiO<sub>2</sub> and the PC-0.03TiO<sub>2</sub>/ODA-90-laser. As depicted in Fig. 4(a), the survey XPS spectra reveal that the C1s and O1s, detected at 284 eV and 531 eV, are the main elements of PC. After loading ODA, the N1s has also appeared in survey XPS spectra of PC-0.03TiO<sub>2</sub>/ODA-90-laser film, which appears at binding energy of 399 eV. Adding ODA and the laser drilling process introduces a reduction in the O1s peak. The high-resolution spectra of C1s and O1s are shown in Fig. 4(b-e), in which, the C1s consists of three Gaussian functions corresponded to the C-C/C-H (284 eV), C-O (285.5 eV) and C=O (289.8 eV). It is clear that the intensity of C-O and C=O groups are reduced after ODA treatment, providing hydrophobic surface. However, the main compound in both PC-0.03TiO<sub>2</sub> and PC-0.03TiO<sub>2</sub>/ODA-90-laser is C-C/C-H bonds instead of carbon-oxygen bands. The O1s is also separated by two peaks at about 531 eV and 533 eV which are related to C-O and C=O

groups [51]. As summarized in Table 1, the percentage of C=O is reduced after adding ODA and laser processing. As shown in Fig. 1(f), the N1s spectrum only includes a peak at 398.7 eV, assigned to the -NH<sub>2</sub> [52, 53].

**Table 1.** The percentages of different carbon and oxygen bonds.

Sample	C1s			O1s	
	C-C/C-H	C-O	C=O	C-O	C=O
PC-0.03TiO <sub>2</sub>	76.75 %	13.76 %	9.49 %	50.81 %	49.19 %
PC-0.03TiO <sub>2</sub> /ODA-90-laser	87.20 %	10.24 %	2.56 %	60.10 %	39.90 %

**Table 2.** Water contact angle values for nanocomposite films.

Sample	Water contact angle (degree)
PC-TiO <sub>2</sub>	90
PC-TiO <sub>2</sub> -laser	45.4
PC-TiO <sub>2</sub> /ODA-laser-15	103.9
PC-TiO <sub>2</sub> /ODA-laser-30	97.2
PC-TiO <sub>2</sub> /ODA-laser-45	117.5
PC-TiO <sub>2</sub> /ODA-laser-60	113.7
PC-TiO <sub>2</sub> /ODA-laser-90	122.4

Wettability of the nanocomposite films was identified through measurement of the water contact angle (WCA) by the sessile-drop method and compared with each other in environmental conditions. The average contact angle of five droplets was measured for each nanocomposite film and reported in Table 2. Before laser drilling, the WCA value of the prepared PC-TiO<sub>2</sub> film was 90°. The WCA of the PC-TiO<sub>2</sub> film after laser drilling was obtained as 45.4°, indicating hydrophilic behavior of PC-TiO<sub>2</sub>-laser sample. The chemical composition of the surface and surface roughness of solid samples strongly affected on the WCA values. It is obtained that the initial WCA of PC-TiO<sub>2</sub> was reduced after laser drilling, which is due to surface roughness enhancement. The presence of ODA on the laser-drilled PC-TiO<sub>2</sub> can also improve hydrophobicity by increasing the WCA value. The hydrophobicity of the mesh was enhanced with increasing immersing time and the best

result was obtained for PC-TiO<sub>2</sub> mesh immersed in ODA for 90 min. In fact, the ODA creates long hydrocarbon chains on the surface of laser-drilled PC-TiO<sub>2</sub> and enhances the hydrophobicity [54].

## IV. CONCLUSION

In the present study, laser drilling was used as a fast and simple method to create a polymeric mesh with uniform holes. To prepare polymer nanocomposite film, polycarbonate was used as a matrix for dispersing anatase and rutile phases of TiO<sub>2</sub> NPs through a simple physical mixing method. According to SEM images, a regular array of holes was created on the PC-TiO<sub>2</sub> film without any crack. The presence of ODA shells was also confirmed through SEM images and XPS analyses. The laser drilling provided a rough surface and adding ODA cover created long hydrocarbon chains on the surface of PC-TiO<sub>2</sub> mesh, changing the hydrophilic surface to hydrophobic. The as-prepared hydrophobic mesh can be used as a filter to remove nonpolar pollutants such as oil from water.

## ACKNOWLEDGMENT

We gratefully acknowledge from Iranian Nano Council and Bu-Ali Sina University for supporting this work.

## REFERENCES

- [1] G. Chen, T. Ushida, and T. Tateishi, "A hybrid network of synthetic polymer mesh and collagen sponge," *Chem. Commun.*, pp. 1505-1506, 2000.
- [2] E. Rebollar, D. Cordero, A. Martins, S. Chiussi, R.L. Reis, N.M. Neves, and B. León, "Improvement of electrospun polymer fiber meshes pore size by femtosecond laser irradiation," *Appl. Surf. Sci.*, Vol. 257, pp. 4091-4095, 2011.
- [3] M. Gong, L. Zhang, and P. Wan, "Polymer nanocomposite meshes for flexible electronic devices," *Prog Polym Sci.*, Vol. 107, pp. s101279(1-33), 2020.
- [4] C. Cazan, A. Enesca, and L. Andronic, "Synergic effect of TiO<sub>2</sub> filler on the

- mechanical properties of polymer nanocomposites,” *Polymers*, Vol. 13, pp. 1-24 2021.
- [5] S. Fu, Z. Sun, P. Huang, Y. Li, and N. Hu, “Some basic aspects of polymer nanocomposites: A critical review,” *Nano Mater, Sci.*, Vol. 1, pp. 2-30, 2019.
- [6] J. Fawaz and V. Mittal, *Synthesis of polymer nanocomposites: review of various techniques*, Synth. Tech. polymer nanocomp., Chap. 1, pp. 1-30, 2014.
- [7] B. Jaleh, S. Hamzehi, R. Sepahvand, S. Azizian, M. Eslamipannah, R. Golbedaghi, A. Meidanchi, and R. Fausto, “Preparation of Polycarbonate-ZnO Nanocomposite Films: Surface Investigation after UV Irradiation,” *Molecules*, Vol. 27, pp. 4448(1-13), 2022.
- [8] B. Jaleh, N. Shahbazi, and A. Jabbari, “Optical and thermal properties of polycarbonate-TiO<sub>2</sub> nanocomposite film,” *Synth. React. Inorg. Met.-Org. Nano-Met. Chem.*, Vol. 46, pp. 602-607, 2016.
- [9] R. Fateh, R. Dillert, and D. Bahnemann, “Preparation and characterization of transparent hydrophilic photocatalytic TiO<sub>2</sub>/SiO<sub>2</sub> thin films on polycarbonate,” *Langmuir*, Vol. 29, pp. 3730-3739, 2013.
- [10] A. Eslami, M.M. Amini, A. Asadi, A.A. Safari, and N. Daglioglu, “Photocatalytic degradation of ibuprofen and naproxen in water over NS-TiO<sub>2</sub> coating on polycarbonate: Process modeling and intermediates identification,” *Inorg. Chem. Commun.*, Vol. 115, pp. 107888(1-9), 2020.
- [11] R. Fateh, A.A. Ismail, R. Dillert, and D.W. Bahnemann, “Highly active crystalline mesoporous TiO<sub>2</sub> films coated onto polycarbonate substrates for self-cleaning applications,” *J. Phys. Chem. C*, Vol. 115, pp. 10405-10411, 2011.
- [12] R. Fateh, R. Dillert, and D. Bahnemann, “Self-cleaning properties, mechanical stability, and adhesion strength of transparent photocatalytic TiO<sub>2</sub>-ZnO coatings on polycarbonate,” *ACS Appl. Mater. Interfaces*, Vol. 6, pp. 2270-2278, 2014.
- [13] B. Jaleh and N. Shahbazi, “Surface properties of UV irradiated PC-TiO<sub>2</sub> nanocomposite film,” *Appl. Surf. Sci.*, Vol. 313, pp. 251-258, 2014.
- [14] Y. Zhao, P. Ding, C. Ba, A. Tang, N. Song, Y. Liu, and L. Shi, “Preparation of TiO<sub>2</sub> coated silicate micro-spheres for enhancing the light diffusion property of polycarbonate composites,” *Displays*, Vol. 35, pp. 220-226, 2014.
- [15] N. Vidakis, M. Petousis, N. Mountakis, S. Grammatikos, V. Papadakis, J. Kechagias, and S. Das, “On the thermal and mechanical performance of Polycarbonate/Titanium Nitride nanocomposites in Material Extrusion Additive Manufacturing,” *Compos. C*, Vol. 8, pp. 100291(1-14), 2022.
- [16] B.K. Deka and T.K. Maji, “Effect of TiO<sub>2</sub> and nanoclay on the properties of wood polymer nanocomposite,” *Compos. A: Appl. Sci. Manuf.*, Vol. 42, pp. 2117-2125, 2011.
- [17] H. Nawaz, M. Umar, R. Maryam, I. Nawaz, H. Razzaq, T. Malik, and X. Liu, “Polymer Nanocomposites based on TiO<sub>2</sub> as a reinforcing agent: An Overview,” *Adv. Eng. Mater.*, Vol. 24, pp. 2200844(1-20), 2022.
- [18] S. Jafari, S. Azizian, and B. Jaleh, “Enhancement of methyl violet removal by modification of TiO<sub>2</sub> nanoparticles with AgI,” *J. Ind. Eng. Chem.*, Vol. 18, pp. 2124-2128, 2012.
- [19] H. Mansour, E.M.A.E. Halium, N.F. Alrasheedi, M.S. Zoromba, and A.F. Al-Hossainy, “Physical properties and DFT calculations of the hybrid organic polymeric nanocomposite thin film [P (An+ o-Aph)+ Glycine/TiO<sub>2</sub>/] HNC with 7.42% power conversion efficiency,” *J. Mol. Struct.*, Vol. 1262, pp. 133001(1-17), 2022.
- [20] M.S. Rafique, M.B. Tahir, M. Rafique, and M. Shakil, “Photocatalytic nanomaterials for air purification and self-cleaning,” in: *Nanotechnology and Photocatalysis for Environmental Applications*, Elsevier, pp. 203-219, 2020.
- [21] K. Wang, Z. Wei, C. Colbeau-Justin, A. Nitta, E. Kowalska, “P25 and its components-electronic properties and photocatalytic activities,” *Surf. Interfaces*, Vol. 31, pp. 102057(1-11), 2022.
- [22] B. Xin, and J. Hao, “Reversibly switchable wettability,” *Chem. Soc. Rev.*, Vol. 39, pp. 769-782, 2010.
- [23] H. Tahzibi and S. Azizian, “Fabrication of superhydrophobic-icephobic carbon cloth

- using polydimethylsiloxane for oil–water separation,” *J. Mol. Liq.*, Vol. 356, pp. 119008(1-9), 2022.
- [24] A. Said, H. Al Abdulgader, D. Alsaeed, Q. Drmosh, T.N. Baroud, and T.A. Saleh, “Hydrophobic tungsten oxide-based mesh modified with hexadecanoic branches for efficient oil/water separation,” *J. Water Process Eng.*, Vol. 49, pp. 102931(1-10), 2022.
- [25] Y. Wu, S. Zhou, and L. Wu, “Fabrication of Robust Hydrophobic and Super-Hydrophobic Polymer Films with Onefold or Dual Inverse Opal Structures,” *Macromol. Mater. Eng.*, Vol. 301, pp. 1430-1436, 2016.
- [26] A.S. Anjum, K.C. Sun, M. Ali, R. Riaz, and S.H. Jeong, “Fabrication of coral-reef structured nano silica for self-cleaning and super-hydrophobic textile applications,” *Chem. Eng. J.*, Vol. 401, pp. 125859(1-9), 2020.
- [27] S. Xiao, X. Hao, Y. Yang, L. Li, N. He, and H. Li, “Feasible fabrication of a wear-resistant hydrophobic surface,” *Appl. Surf. Sci.*, Vol. 463, pp. 923-930, 2019.
- [28] B. Luo, P.W. Shum, Z. Zhou, and K. Li, “Preparation of hydrophobic surface on steel by patterning using laser ablation process,” *Surf. Coat. Tech.*, Vol. 204, pp. 1180-1185, 2010.
- [29] L. Xu, R.G. Karunakaran, J. Guo, and S. Yang, “Transparent, superhydrophobic surfaces from one-step spin coating of hydrophobic nanoparticles,” *ACS Appl. Mater. Interfaces*, Vol. 4, pp. 1118-1125, 2012.
- [30] V.S. Saji, “Superhydrophobic surfaces and coatings by electrochemical anodic oxidation and plasma electrolytic oxidation,” *Adv. Colloid Interface Sci.*, Vol. 283, pp. 102245(1-27), 2020.
- [31] M.H. Kwon, H.S. Shin, and C.N. Chu, “Fabrication of a super-hydrophobic surface on metal using laser ablation and electrodeposition,” *Appl. Surf. Sci.*, Vol. 288, pp. 222-228, 2014.
- [32] M. Ma, Y. Mao, M. Gupta, K.K. Gleason, and G.C. Rutledge, “Superhydrophobic fabrics produced by electrospinning and chemical vapor deposition,” *Macromolecules*, Vol. 38, pp. 9742-9748, 2005.
- [33] M. Poddighe and P. Innocenzi, “Hydrophobic thin films from sol–gel processing: A critical review,” *Materials*, Vol. 14, pp. 6799(1-18), 2021.
- [34] J. Du, X. Luo, Z. Fu, C. Xu, X. Ren, W. Gao, and Y. Li, “Improving the hydrophobicity of nylon fabric by consecutive treatment with poly (acrylic acid), tetraethylorthosilicate, and octadecylamine,” *J. Appl. Polym. Sci.*, Vol. 132, pp. 42456(1-7), 2015.
- [35] M.K. Mehrizi and Z. Shahi, *A Review on Hydrophobicity and Fabricating Hydrophobic Surfaces on the Textiles*, Sustainable Practices in the Textile Industry, Vol. 1, Chap. 6, pp. 149-165, 2021.
- [36] M. Sun, H. Guo, J. Zheng, Y. Wang, X. Liu, Q. Li, R. Wang, and X. Jia, “Hydrophobic octadecylamine-polyphenol film coated slow released urea via one-step spraying co-deposition,” *Polym. Test.*, Vol. 91, pp. 106831(1-8), 2020.
- [37] Y. Chen, J. Xu, L. Shen, J. Zhao, J. Chen, Y. Yang, L. Wang, J. Zhao, and C. Wang, “Tunable wettability of jet electrodeposited micro-nano structures modified by laser radiation,” *Surf. Coat. Tech.*, Vol. 446, pp. 128763(1-9), 2022.
- [38] N.S. Kasalkova, P. Slepicka, Z. Kolska, and V. Svorcik, *Wettability and other surface properties of modified polymers*, Wetting Wettability, pp. 323-356, 2015.
- [39] Z. Yang, X. Liu, and Y. Tian, “Insights into the wettability transition of nanosecond laser ablated surface under ambient air exposure,” *J. Colloid Interface Sci.*, Vol. 533, pp. 268-277, 2019.
- [40] M. Liu, Z. Yang, L. Dong, Z. Wang, S. Wang, L. Wang, Y. Xie, Q. Zhang, Z. Weng, and Y. Tian, “Vacuum conditions for tunable wettability transition on laser ablated Ti-6Al-4V alloy surfaces,” *Colloids Surf. A Physicochem. Eng. Asp.*, Vol. 647, pp. 129023(1-8), 2022.
- [41] G. Dogan, F. Chiu, S.U. Chen, M.R. David, A. Michalowski, M. Schaezel, C. Silber, G. Schuetz, C. Grevent, and K. Keskinbora, “Micromachining of Al<sub>2</sub>O<sub>3</sub> thin films via laser drilling and plasma etching for interfacing copper,” *Mater. Des.*, Vol. 210, pp. 110114(1-11), 2021.

- [42] G.D. Gautam and A.K. Pandey, "Pulsed Nd: YAG laser beam drilling: A review," *Opt. Laser Technol.*, Vol. 100, pp. 183-215, 2018.
- [43] N. Masmiati and P. Philip, "Investigations on laser percussion drilling of some thermoplastic polymers," *J. Mater. Process. Technol.*, Vol. 185, pp. 198-203, 2007.
- [44] S. Sharma, V. Mandal, S. Ramakrishna, and J. Ramkumar, "Numerical simulation of melt hydrodynamics induced hole blockage in Quasi-CW fiber laser micro-drilling of TiAl6V4," *J. Mater. Process. Technol.*, Vol. 262, pp. 131-148, 2018.
- [45] A.E. Abdulwahab, K.A. Hubeatir, and K.I. Imhan, "A comparative study on the effect of CO<sub>2</sub> laser parameters on drilling process of polycarbonate and PMMA polymers complemented by design expert," *Eng. Res. Express.*, Vol. 4, pp. 045029(1-8), 2022.
- [46] T. Meunier, S.G. Gopalakrishnan, and A. Weck, "Plane stress local failure criterion for polycarbonate containing laser drilled microvoids," *Polymer*, Vol. 54, pp. 1530-1537, 2013.
- [47] N. Bakhtiari, S. Azizian, B.F. Mohazzab, and B. Jaleh, "One-step fabrication of brass filter with reversible wettability by nanosecond fiber laser ablation for highly efficient oil/water separation," *Sep. Purif. Technol.*, Vol. 259, pp. 118139(1-12), 2021.
- [48] S. Ravi-Kumar, B. Lies, X. Zhang, H. Lyu, and H. Qin, "Laser ablation of polymers: A review," *Polym. Int.*, Vol. 68, pp. 1391-1401, 2019.
- [49] D.J. da Silva, M.T. Escote, S.A. Cruz, D.F. Simião, A. Zenatti, and M.S. Curvello, "Polycarbonate/TiO<sub>2</sub> nanofibers nanocomposite: Preparation and properties," *Polym. Compos.*, Vol. 39, pp. E780-E790, 2018.
- [50] Z. Tang, C. Youshuang, and W. Mouhua, "Specific properties improvement of polycarbonate induced by irradiation at elevated particular temperature," *Radiat. Phys. Chem.*, Vol. 96, pp.171-175, 2014.
- [51] A. Qureshi, S. Shah, S. Pelagade, N. Singh, S. Mukherjee, A. Tripathi, U. Despande, and T. Shripathi, "Surface modification of polycarbonate by plasma treatment," in: *J. Phys: Conf. Series*, IOP Publishing, pp. 012108(1-7), 2010.
- [52] J. Oviedo, M.A. San-Miguel, J.A. Heredia-Guerrero, and J.J. Benítez, "Electrostatic induced molecular tilting in self-assembled monolayers of n-octadecylamine on mica," *J. Phys. Chem. C*, Vol. 116, pp. 7099-7105, 2012.
- [53] J. Benítez, M. San-Miguel, S. Domínguez-Meister, J. Heredia-Guerrero, and M. Salmeron, "Structure and chemical state of octadecylamine self-assembled monolayers on mica," *J. Phys. Chem. C*, Vol. 115, pp. 19716-19723, 2011.
- [54] Y. Yu, Q. Wang, J. Yuan, X. Fan, P. Wang, and L. Cui, "Hydrophobic modification of cotton fabric with octadecylamine via laccase/TEMPO mediated grafting," *Carbohydr. Polym.*, Vol. 137, pp. 549-555, 2016.



**Soheil Mohammadtaheri** was born in Iran. He received his M.Sc. degree in Optics and Laser in 2016 and his Ph.D. degree in the same field in 2022. His research interests mainly focus on laser-assisted modification of membranes and the fabrication of mesh structures for engineering application.



**Prof. Babak Jaleh** received his Ph.D. in 2004 from Amirkabir University of Technology, Tehran, Iran. He is a Professor of Physics (Optics and Laser) at Bu-Ali Sina University, Hamedan, Iran. He has published over 160 research articles with more than 6,600 citations and has been listed among Stanford University's Top 2% World Scientists from

2019 to 2024. He is the Head of the Central Laboratory and leads the Laser and Nanocomposite Laboratory at Bu-Ali Sina University.



**Mahtab Eslamipannah** received her M.Sc. degree in Optics and Laser from Bu-Ali Sina University, Hamedan, Iran, in 2020 and her Ph.D. degree in the same field in 2025 under the supervision of Prof. Babak Jaleh. Her research focuses on the fabrication and modification of catalysts for environmental and electrochemical applications.



**Niloufar Pakzad Afshar** has received her M.Sc. degree in 2004 from Urmia University, Urmia, Iran. She is a part time instructor of

Islamic Azad University and part time researcher of Iran Telecom Research Center. Her research focuses on optical devices.



**Saeid Azizian** received his Ph.D. in 2000 from Sharif University of Technology, Tehran, Iran. Presently, he is a professor of Physical Chemistry at Bu Ali Sina University, Hamedan, Iran. He has published over 219 research articles (citations>12000). He is also included in Stanford University's "Ranking of the World Scientists: World's Top 2% Scientists" from 2019 to 2024. He is the head of physical chemistry Lab at the Faculty of Chemistry.